

# Measurement of titanium surface roughness created by non-conventional cutting technology

J. RUSNÁK<sup>1</sup>, M. ZELENÁK<sup>2</sup>, J. VALÍČEK<sup>2</sup>, M. KADNÁR<sup>1</sup>, S. HLOCH<sup>3</sup>, P. HLAVÁČEK<sup>2</sup>, M. KUŠNEROVÁ<sup>2</sup>, R. ČEP<sup>4</sup>, J. KADNÁR<sup>5</sup>

<sup>1</sup>*Faculty of Engineering, Slovak University of Agriculture in Nitra, Nitra, Slovak Republic*

<sup>2</sup>*Faculty of Mining and Geology, VŠB-Technical University of Ostrava, Ostrava, Czech Republic*

<sup>3</sup>*Faculty of Manufacturing Technologies, Technical University of Košice, Košice, Slovak Republic*

<sup>4</sup>*Faculty of Mechanical Engineering, VŠB-Technical University of Ostrava, Ostrava, Czech Republic*

<sup>5</sup>*Faculty of Materials Science and Technology, Slovak University of Technology in Bratislava, Bratislava, Slovak Republic*

## Abstract

RUSNÁK J., ZELENÁK M., VALÍČEK J., KADNÁR M., HLOCH S., HLAVÁČEK P., KUŠNEROVÁ M., ČEP R., KADNÁR J., 2011. **Measurement of titanium surface roughness created by non-conventional cutting technology.** Res. Agr. Eng., 57 (Special Issue): S57–S60.

The paper evaluates the surface roughness quality of the titanium samples created by abrasive waterjet (AWJ) and by CO<sub>2</sub> laser beam cuttings. The introduction describes the principle of the mechanical (contact) method as well as the roughness parameters used for the experiment results evaluation. The following parts summarise the experimental conditions and the measurement methodology. The emphasis of this work is laid on the comparison of machined surfaces final quality for the selected traverse speeds.

**Keywords:** surface properties; metrology; titanium alloy; roughness measurement

The surface quality control is a very important part of the surface preparation in all types of technologies that are used for their creation (VALÍČEK et al. 2009). Since 1930, when topography meters were invented, great progress has been made in both the methods and measuring equipment. The digital methods implemented in 1960s have enabled the surface evaluation by 3D method (BUMBÁLEK et al. 1989).

## MATERIAL AND METHODS

The standardisation of the surface roughness is both a technical and an economic task. Thus, its importance is increasing with the requirements for the precision, efficiency and reliability of the machine components and equipment. All the requirements mentioned depend on many parameters of roughness, mechanical characteristics of the functional surfaces

---

Supported by Student Grant Competition, Project No. SP2011/78, SP/201058, Czech Science Foundation, Grant No. 101/09/0650, Ministry of Education, Youth and Sports of the Czech Republic, Project No. MSM 6198910016, Regional Research Center of Materials and Technology, Project No. CZ.1.05/2.1.00/01.0040, Institute of Clean Technologies for Extraction and Utilization of Energy Resources, Project No. CZ.1.05/2.1.00/03.0082.

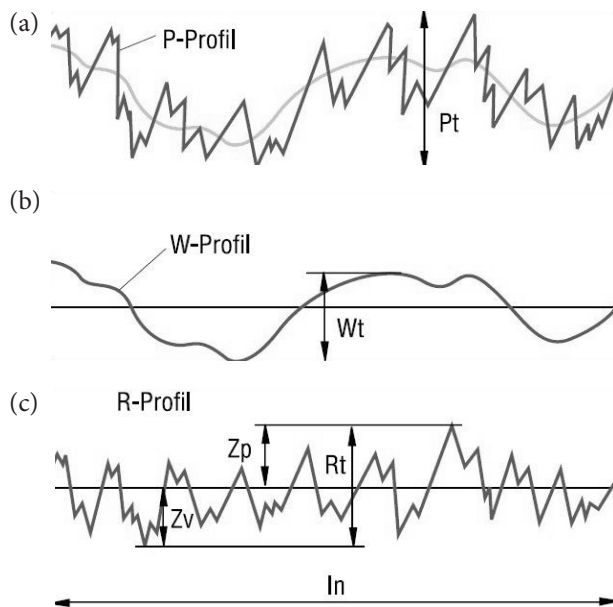


Fig. 1. The profiles according to ČSN EN ISO 4287 (1999) (a) *P* – profile, (b) *W* – profile, (c) *R* – profile

and the method of assembling. The main reason is to improve the lifetime and operational characteristics of the engineering products (BUMBÁLEK et al. 1989).

According to the ČSN EN ISO 4287 (1999) standard, the following surface profiles are distinguished; the basic surface profile *P* (Fig. 1a), the surface waviness profile *W* (Fig. 1b) and the surface roughness profile *R* (Fig. 1c). The basic profile is an ideal smooth surface. The waviness profile is characterised by low frequencies and high amplitudes of the surface roughness. The roughness profile is characterised by high frequencies and low amplitudes of the surface roughness.

The middle arithmetic aberrance of the *Ra* profile is the primary parameter of the surface roughness. It is the average arithmetic value of absolute profile aberrances in the length range. It reflects the time and dimensional dependence of the surface roughness and is determined by the following Eq. 1:

$$Ra = \frac{1}{l_p} \int_0^{l_p} |y(x)| dx \quad \text{or} \quad Ra \approx \frac{1}{n} \sum_{i=1}^n |y(x_i)| \quad (1)$$

where

$l_p$  – measured length (m)

$y(x)$  – profile dependence (BUMBÁLEK et al. 1989)

$y(x_i)$  – coordinates of  $n$  points (BUMBÁLEK et al. 1989) in the length range,  $i = 1, 2, \dots, n$

The mechanical (contact) method is currently the most used method mainly in engineering (Fig. 2). Its advantage is the direct measurement and the possibility of its use for all surface types (HLAVÁČEK et

al. 2009). The analogue recording of the surface topography which is the result of this method can be transformed into digital recording. The values measured by this method are also used in other types of methods (for comparison, etc.). The method also allows measuring the geometric profile of the surface repeatedly and identically (ZELEŇÁK et al. 2009). However, the pressure generated on the prick sensor causes elastic and plastic deformation in the surface layer. The total deformation depends on the surface hardness. Thus, the prick sensor damages the measured surface which influences not only the evaluated surface but also the whole measuring.

As the initial material for the experimental purposes, unalloyed titanium was used with the specification ASTM B265-99 (1999), supplied in the annealed condition. The chemical and mechanical parameters of the titanium are given in Table 1.

Fig. 3 illustrates the cutting heads of the abrasive waterjet (AWJ) and CO<sub>2</sub> laser beams. The technological parameters for the cuttings are given in Table 2.

The surfaces created by AWJ and CO<sub>2</sub> laser beam cutting technologies were measured with a contact profilometer SurfTest SJ 401 (Mitutoyo America Corporation, Aurora, USA) (Fig. 4). Each sample was measured in 19 depth traces. The results of the surface irregularities from each trace were obtained, analysed and statistically processed. The measurement was performed on five consecutive fundamental lengths ( $l_r = 2.5$  mm) and the average value of the surface profile roughness *Ra* was determined from the results obtained.

## RESULTS AND DISCUSSION

The comparison of the roughness parameters obtained by the AWJ and CO<sub>2</sub> laser cutting technologies (Fig. 5) shows that the AWJ technology achieved five times lower *Ra* values than were those obtained with CO<sub>2</sub> laser cutting, thus indicating that the AWJ

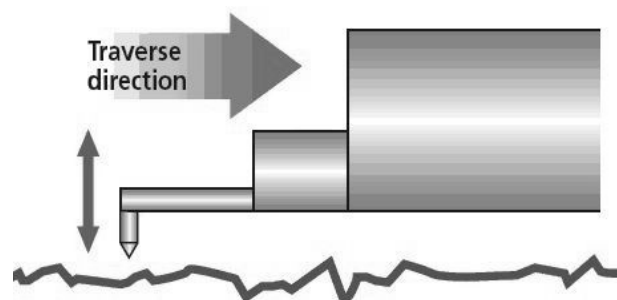


Fig. 2. The principle of sensor contact profilometer

Table 1. Chemical and mechanical parameters of ASTM B265-99

Fe	C	O	H	N
0.2% max	0.08% max	0.18% max	0.015% max	0.03% max
Yield strength 0.2%		Yong's module		Elongation %
172–310 MPa		103 GPa		25–37

Table 2. Experimental parameters of abrasive waterjet (AWJ) and CO<sub>2</sub> laser beam cuttings

Technological parameter	AWJ			Technological parameter	CO <sub>2</sub> laser		
	Sign	Unit	Value		Sign	Unit	Value
Liquid pressure	$p$	MPa	370	pressure of inert gas	$p_g$	MPa	1.7
Water orifice diameter	$d_o$	mm	0.3	power	$P$	W	3,500
Focusing tube diameter	$d_f$	mm	0.8	traverse speed	$v$	mm/min	350, 450, 550
Focusing tube length	$l_a$	mm	76	standoff distance	$z$	mm	1.5
Abrasive mass flow rate	$m_a$	g/min	250	diameter of beam	$d$	mm	2
Standoff distance	$z$	mm	4	output speed of gas	$v_p$	mm/min	800, 500, 500
Traverse speed	$v$	mm/min	350, 450, 550	type of inert gas	$N_2$	–	nitrogen
Abrasive size	–	MESH	80	frequency	$f$	Hz	0

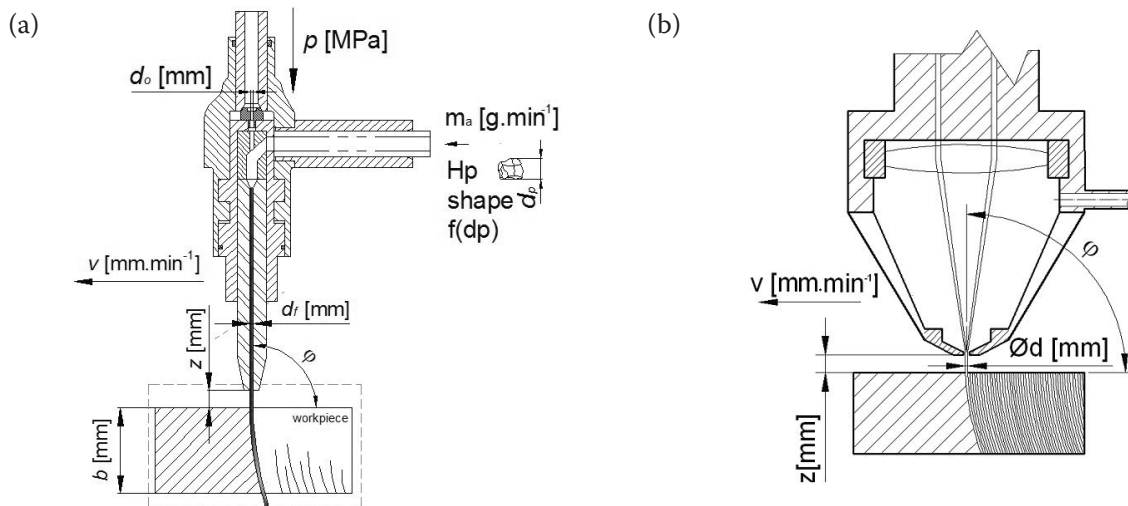


Fig. 3. Details of the cutting head with the target material (a) abrasive waterjet cutting (b) CO<sub>2</sub> laser beam cutting

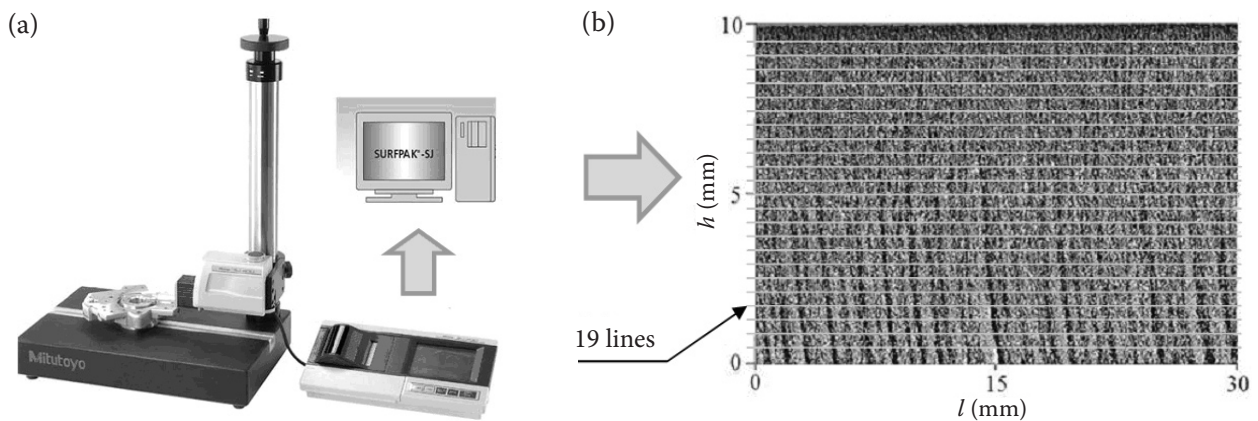


Fig. 4. (a) Contact profilometer SURFTEST SJ 401, (b) photo of the surface measured in 19 lines

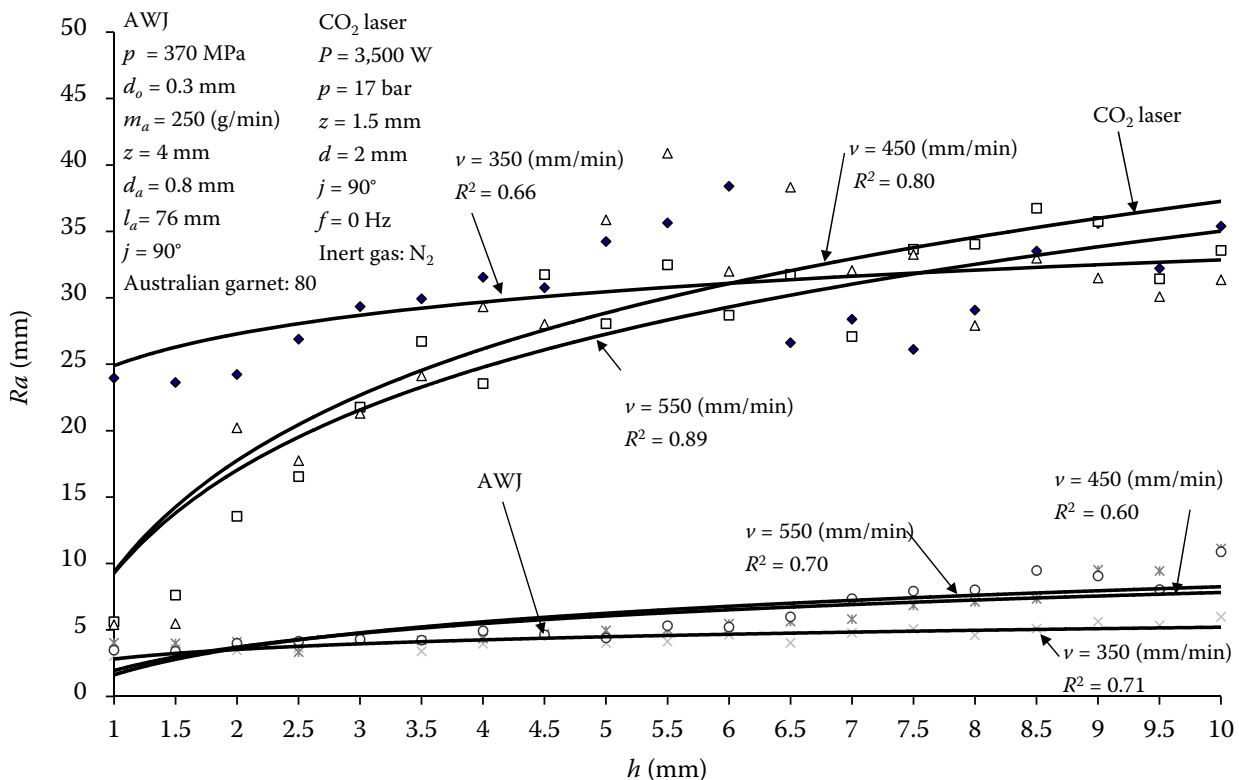


Fig. 5. The dependence of the surface roughness parameter  $Ra$  on the depth of cut  $h$  for AWJ and  $CO_2$  laser beam cuttings

technology provides a significantly higher quality of the machined surfaces. The  $CO_2$  laser beam cutting technology shows significant differences in the curve behaviour as compared to AWJ technology.

According to Fig. 5, the surface roughness increases with the increasing traverse speed. The behaviour of the curve in AWJ technology shows minimal differences and smooth behaviour at particular speeds, which indicates good optimisation of the cutting process and an appropriate setup of the input.

#### Acknowledgement

We would also like to thank the Moravian-Silesian Region 01737/2010/RRC for financial support.

#### References

ASTM B265-99, 1999. Standard Specification for Titanium and Titanium Alloy Strip, Sheet, and Plate. Available at <http://www.astm.org/Standards/B265.htm>

BUMBÁLEK B., OBVODY V., OŠŤÁDAL B., 1989. Drsnost povrchu (Surface Roughness). Prague, SNTL.

ČSN EN ISO 4287, 1999. Geometrické požadavky na výrobky (GPS) – Struktura povrchu: Profilová metoda – Termíny, definice a parametry struktury povrchu (Geometrical product specifications (GPS) – Surface texture: Profile method – Terms, definitions and surface texture parameters).

HĽAVÁČEK P., VALÍČEK J., HLOCH S., GREGER M., FOLDYNA J., IVANDIČ Ž., SITEK L., KUŠNEROVÁ M., ZELENÁK M., 2009. Measurement of fine grains copper surface texture created by abrasive waterjet cutting. *Strojárstvo*, 51: 273–380.

VALÍČEK J., HLOCH S., KOZAK D., 2009. Study of Surface Topography Created by Abrasive Waterjet Cutting. *Slovanski Brod, Strojarski Fakultet u Slovanskom Brodu*.

ZELENÁK M., VALÍČEK J., HLOCH S., HREHA P., ČEPOVÁ L., 2009. Analogy of abrasive waterjet technology with classical technologies. *Technologické inžinierstvo*, 6: 84–87.

Received for publication December 7, 2010

Accepted after corrections April 7, 2011

Corresponding author:

doc. Ing. MILAN KADNÁR, Ph.D., Slovak University of Agriculture in Nitra, Faculty of Engineering, Department of Machine Design, Tr. A. Hlinku 2, 949 76 Nitra, Slovak Republic  
phone: + 421 376 414 107, e-mail: milan.kadnar@uniag.sk